



Cite this: *Chem. Commun.*, 2020, 56, 1952

Received 6th December 2019,
Accepted 13th January 2020

DOI: 10.1039/c9cc09510a

rsc.li/chemcomm

Computational investigation of chalcogenide spinel conductors for all-solid-state Mg batteries†

Julius Koettgen,^a Christopher J. Bartel^b and Gerbrand Ceder^{*ab}

Seven MgLn_2X_4 (Ln = lanthanoid, X = S, Se) spinels are calculated with density functional theory to have low barriers for Mg migration (<380 meV) and are stable or nearly stable (within 50 meV per atom of stability with respect to competing structures and compositions). As the size of the Ln increases, Mg mobility is found to increase, but stability in the spinel structure is found to decrease.

Magnesium batteries are an interesting alternative to Li-ion technology because of the potential for improved safety and higher energy density.^{1–3} The ability to use Mg metal as an anode is beneficial because of its high volumetric energy density (3830 mA h mL^{−1}) relative to that of graphite (700 mA h mL^{−1}), which is generally employed as an anode in Li-ion batteries using liquid or polymer gel electrolytes.⁴ Only a few good liquid electrolytes exist for Mg batteries as Mg metal cannot be deposited reversibly in electrolytes that react with the metal. For this reason, we recently explored whether solid electrolytes with sufficient Mg-ion conductivity exist.⁵ Unlike for Li and Na, for which a large number of solids with very high ionic conductivity have been reported,^{6,7} virtually no solids with high Mg-ion conductivity have been identified, apart from a few so-far unconfirmed computational predictions.⁸

Materials with high Li conductivity have been shown to possess low Mg mobility because the higher charge density of divalent Mg relative to that of monovalent Li leads to stronger electrostatic interactions with the host lattice.⁹ Recently, two design principles to improve mobility in multivalent solids have been proposed. First, structures where the multivalent ion sits in a site where it has an unfavourable coordination environment have been observed to have lower migration barriers, in particular when the activated state is closer to the

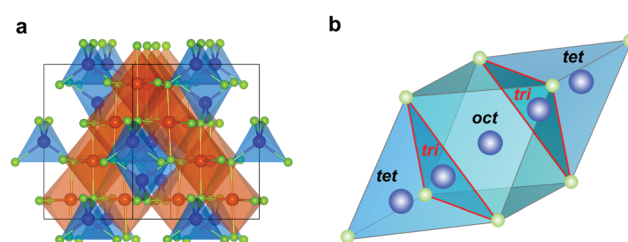


Fig. 1 (a) MgLn_2X_4 spinel structure where Mg is blue, the lanthanoid (Ln) is orange, and the chalcogenide (X) is light green, (b) Diffusion path for Mg^{2+} (blue) from the tetrahedral site, tet, through the face-sharing triangular state, tri, then the octahedral site, oct. The diffusion path is locally symmetric such that before returning to tet, Mg^{2+} again passes through tri.

preferred coordination.^{7,9–11} Superior Mg^{2+} mobility was previously observed in spinels (Fig. 1a) with composition TM_2X_4 (TM = Ti, Cr, Mn, Fe, Co, Ni and X = O, S), where the diffusing ion resides in a tetrahedral site but migrates through an activated octahedral coordination as shown in Fig. 1b.^{9,10,12–14} Second, Mg^{2+} mobility is generally higher for sulphides than oxides, suggesting that the inclusion of larger, more polarizable anions helps decrease the electrostatic interaction between the working ion and the host structure.^{10,14}

These design principles led to the investigation of magnesium spinel chalcogenides MgM_2X_4 with M = Sc, In, Y and X = S, Se, Te.⁵ Several of these compositions have been reported experimentally, including MgSc_2S_4 ,¹⁵ MgIn_2S_4 ,^{15,16} MgSc_2Se_4 ,¹⁷ and MgY_2Se_4 .¹⁷ The calculated barriers for Mg^{2+} migration generally decrease from sulphides to selenides to tellurides as both the unit cell volume and the polarizability of the anion increase. In MgSc_2Se_4 , *ab initio* calculations and nuclear magnetic resonance experiments indicate a Mg^{2+} migration barrier of 380 meV, comparable to barriers in Li-ion cathode materials.¹⁸ In this work, we demonstrate that Mg^{2+} mobility can be further increased through the incorporation of large cations from the lanthanide series. However, destabilization of the spinel structure occurs upon increasing the size of the lanthanoid; therefore, the optimal spinel Mg conductor balances high mobility and synthesizability.

^a Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, CA 94720, USA. E-mail: gceder@berkeley.edu

^b Department of Materials Science and Engineering, University of California, Berkeley, CA 94720, USA

† Electronic supplementary information (ESI) available: Table of calculated results. See DOI: 10.1039/c9cc09510a

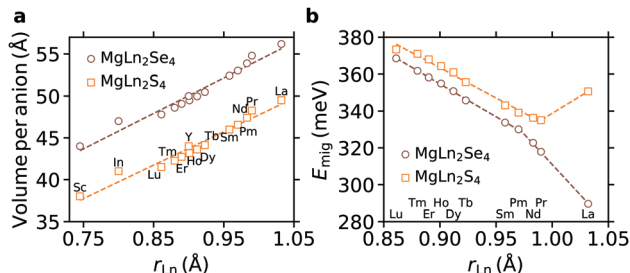


Fig. 2 (a) Effect of Ln ionic radius, r_{Ln} , on the calculated unit cell volume of the spinel structure, (b) Effect of r_{Ln} on the vacancy-mediated Mg^{2+} migration barrier, E_{mig} . Ionic radii are from Shannon.²² Results for Sc, In, and Y are from ref. 5. In both panels, the dashed lines are drawn to guide the eye.

The Mg^{2+} mobility and stability of magnesium chalcogenide spinels, $MgLn_2X_4$, with $Ln = Lu, Tm, Er, Ho, Dy, Tb, Sm, Pm, Nd, Pr, La$ and $X = S, Se$ were investigated using density functional theory (DFT) in the generalized gradient approximation (GGA)¹⁹ and the nudged elastic band method (NEB)²⁰ for Mg^{2+} mobility calculations. Meta-GGA²¹ was used for stability calculations. Substituting larger lanthanoids into the spinel increases the unit cell volume, as shown in Fig. 2a. A 40% increase of the cation radius, r_{Ln} , from 0.745 Å (Sc^{3+})²² to 1.032 Å (La^{3+}),²² leads to a unit cell volume increase of ~30%. Fig. 2b shows the calculated Mg^{2+} migration barrier in these spinels assuming vacancy-mediated diffusion. The increase in volume to accommodate larger cations does indeed correlate with an improved Mg^{2+} mobility, as the calculated migration barriers decrease from 375 meV for $MgSc_2Se_4$ ⁵ to 290 meV for $MgLa_2Se_4$. In fact, the barriers calculated for all materials are lower than that of the previously synthesized $MgSc_2Se_4$. The Mg^{2+} migration barrier decreases nearly linearly with r_{Ln} , with the notable exception of $MgLa_2S_4$, which is associated with the destabilization of Mg in the octahedral state as discussed later.

The energy profiles along the Mg^{2+} migration path are shown in Fig. 3. All compounds show a global minimum with Mg in a tetrahedral site (tet), confirming that it is a locally stable site in these spinel structures. All compounds except $MgLa_2S_4$ show a local minimum for the octahedral state (oct), and the

transition state (highest energy along the path) occurs when Mg^{2+} passes through the triangular face (tri) that is shared between tet and oct. Of particular importance for Mg^{2+} migration is the distance between the migrating Mg^{2+} and neighbouring chalcogenides (X), as the electron density of these anions impedes cation transport. Assuming regular polyhedra, the minimum distance between the centroid (Mg^{2+}) and vertex (X^{2-}) of each environment is proportional to $\frac{d_{XX}}{\sqrt{3}} \approx 0.57d_{XX}$, $\frac{3d_{XX}}{2\sqrt{6}} \approx 0.61d_{XX}$,

and $\frac{d_{XX}}{\sqrt{2}} \approx 0.71d_{XX}$ for tri, tet, and oct, respectively, where d_{XX} is the X-X bond distance that forms the shared edge of the octahedron and tetrahedron. This relationship dictates that tri will have the smallest Mg-X distance and therefore likely be the highest energy (transition) state as long as oct and tet are local minima in the energy profile. For $MgLa_2S_4$, oct is not a local minimum and the migration barrier for this material is therefore determined by $E_{oct} - E_{tet}$.

The Mg^{2+} migration energy, E_{mig} , is compared to the energy of the octahedral state relative to the tetrahedral state ($E_{oct} - E_{tet}$) in Fig. 4. The energies of the tri and oct states (relative to tet) change in opposite directions as the structure expands to accommodate larger and larger Ln's. tri is stabilized with increasing r_{Ln} because this state requires unfavourably small Mg-X distances as Mg^{2+} passes through the triangular face, and structure expansion lengthens this distance. The destabilization of oct when r_{Ln} is increased can be attributed to the relatively small size of Mg^{2+} . This is reflected in the ground-state structures for MgX compounds – MgS is rock salt with octahedral Mg coordination but increasing r_X to $MgSe$ changes the preferred coordination to tetrahedral in wurtzite (ground-state structures determined with GGA). The preference for coordination of a cation, c, by an anion, a, can be estimated by classic radii ratio rules²³ where tetrahedral coordination is expected for $0.225 < r_c/r_a \leq 0.414$ and octahedral coordination for $0.414 < r_c/r_a \leq 0.732$. For Mg^{2+} , the radius ratio is 0.391 for sulphides and 0.364 for selenides, suggesting Mg^{2+} should prefer large tetrahedral or small octahedral environments for these chalcogenides. The octahedral Mg-X bond distance in MgS is ~2.61 Å and expands from ~2.73 (2.85) Å in $MgLu_2S_4$ ($MgLu_2Se_4$) to ~2.85 (2.96) Å in

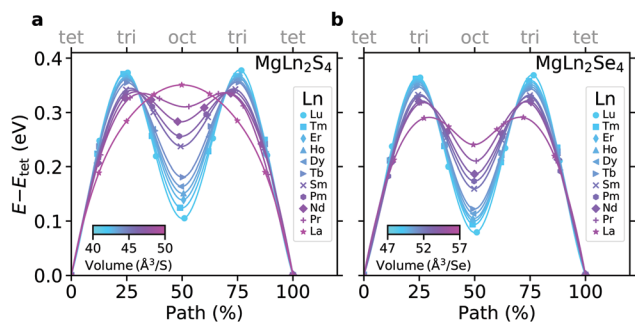


Fig. 3 Energy profiles for vacancy-mediated Mg^{2+} migration in sulphides (a) and selenides (b). Energy is shown relative to the tetrahedral Mg state ($E - E_{tet}$). The colourbar provides the volume per anion of the pristine structure.

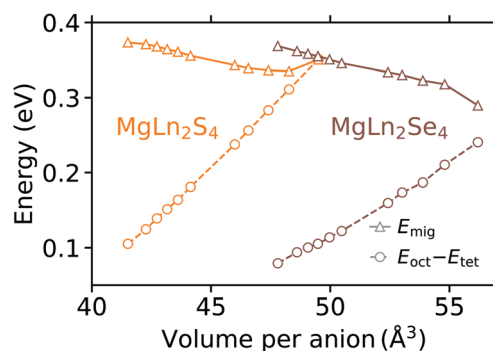


Fig. 4 Comparing the Mg^{2+} migration energy, E_{mig} , to the difference in octahedral and tetrahedral energies, $E_{oct} - E_{tet}$ as a function of the calculated volume per anion in the pristine structures.

MgLa₂S₄ (MgLa₂Se₄) as r_{Ln} increases in these spinels. The unfavourably expanded MgX₆ octahedra in the MgLn₂X₄ spinels accounts for the destabilization of oct relative to tet as r_{Ln} increases.

One of the motivations for studying spinel conductors is that they flatten the migration energy profile by stabilizing tetrahedral Mg and enabling Mg to pass through a more stable octahedral configuration during migration. This principle suggests that minimizing the difference in energy between the oct and tet states would lead to the lowest possible migration barriers because the energy profile is maximally flat when $E_{\text{oct}} = E_{\text{tet}}$. However, within this group of MgLn₂X₄ compounds, we find instead that maximizing this energy difference results in the lowest migration barriers (with the exception of MgLa₂S₄) because the area of the face-sharing triangle is largest (most stable) when the MgX₆ octahedra is largest (least stable).

Finally, the stability of the spinel structure relative to competing polymorphs and competing compounds was investigated using the revised-TPSS meta-GGA density functional.²¹ Meta-GGA's have been shown to be superior to GGA in determining the ground-state structure²⁴ and stability²⁵ of chalcogenides. In Fig. 5, the energy above the convex hull of stable compounds in each chemical space, E_{hull} ,^{14,26} is shown for all compounds in five different structures typically observed for AB₂X₄ compounds.²⁷ Experimentally known structures for each compound are highlighted along the top of Fig. 5. Stable compounds have $E_{\text{hull}} = 0$, and synthesized sulphides and selenides have been observed to be metastable up to $E_{\text{hull}} \approx 50$ meV per atom.²⁸ An even wider range of accessible metastability is expected for spinels because of their especially low surface energy, which may result in preferential nucleation during synthesis.²⁹

MgLu₂S₄, MgLu₂Se₄, MgTm₂Se₄, and MgEr₂Se₄ were calculated to have $E_{\text{hull}} < 25$ meV per atom and spinel as the lowest energy structure at that composition. Additionally, MgTm₂S₄, MgEr₂S₄, and MgHo₂Se₄ have $E_{\text{hull}} < 50$ meV per atom in the spinel structure but MnY₂S₄ is the lowest energy polymorph. On this basis, these seven materials are considered potentially synthesizable in the spinel structure. Indeed, all but MgEr₂S₄ have been reported to crystallize in the spinel structure (MgTm₂S₄ has been reported in both spinel

and MnY₂S₄ structures).^{27,30} Our calculations are generally consistent with the experimental observations as the experimentally observed crystal structure is calculated to be the lowest energy structure at MgLn₂X₄ for 9 of 10 materials (all except MgHo₂Se₄), and all 10 experimentally observed structures are calculated to be stable or nearly stable ($E_{\text{hull}} < 50$ meV per atom).^{27,30}

The calculated sequence of stable crystal structures can be understood by considering the Ln coordination environment. At low r_{Ln} , spinel is the lowest energy structure, then MnY₂S₄ becomes the lowest energy for intermediate r_{Ln} , and the Th₃P₄ structure is the most stable polymorph for the largest Ln's. The Ln coordination number increases from 6 in spinel to 6/7 in MnY₂S₄ to 8 in Th₃P₄, stabilizing the larger and larger Ln. The larger selenium stabilizes spinel for larger Ln, up to at least Ho, whereas spinel is the calculated ground-state only for Ln=Lu among the sulphides.

Increasing the size of the cation in chalcogenide spinels decreases the Mg²⁺ migration barrier. However, increasing the cation size also leads to a preference for non-spinel structures and a general destabilization relative to competing compounds. The spinel structure has the advantage of placing Mg in its less stable tetrahedral configuration, decreasing the Mg migration barrier; however, this advantage is balanced by energetically preferred alternative structures for large cations. Still, we predict MgLu₂S₄, MgLu₂Se₄, MgTm₂S₄, MgTm₂Se₄, MgEr₂S₄, MgEr₂Se₄, and MgHo₂Se₄ to be candidate solid-state electrolytes that strike a balance between relatively small Mg migration energies ($E_{\text{mig}} < 380$ meV) and relatively good stability ($E_{\text{hull}} < 50$ meV per atom) in the spinel structure.

The stability and Mg mobility of the investigated materials were calculated with density functional theory (DFT)³¹ using the Vienna *Ab Initio* Simulation Package (VASP).³² For mobility calculations, the generalized gradient approximation (GGA) according to Perdew, Burke, and Ernzerhof (PBE)³³ and the projector augmented-wave (PAW) method³⁴ were used with an energy cut-off of 520 eV for plane waves. $2 \times 2 \times 2$ supercells, e.g., Mg₁₆La₃₂Se₆₄ and (Mg₁₅La₃₂Se₆₄)²⁻, were calculated using a $2 \times 2 \times 2$ Monkhorst-Pack k -point mesh. The positions of the atoms and the cell volume were optimized for the pristine structure. For the subsequent mobility calculations with one Mg²⁺ vacancy, only the positions of the ions were optimized. Electronic and ionic relaxations were performed with convergence parameters of 10^{-5} eV and 10^{-2} eV Å⁻¹, respectively. The Mg²⁺ vacancy was charge-balanced by a neutralizing background charge. The minimum energy pathways were calculated by linearly interpolating seven images between the optimized initial and final structures and subsequently applying the nudged elastic band (NEB) method.³⁵ For the stability calculations, the revised-TPSS self-consistent meta-GGA³⁶ within the PAW method was used to calculate all MgLn₂X₄ compounds in each of the five prototype structures – spinel, MnY₂S₄, Th₃P₄, olivine, and Yb₃S₄ – and all relevant competing phases available in the Materials Project.³⁷ All calculated results are available as a table in the ESI.†

This work was supported as part of the Joint Center for Energy Storage Research (JCESR), an Energy Innovation Hub funded by the U.S. Department of Energy, Office of Science, Basic Energy Sciences. This work utilized high-performance

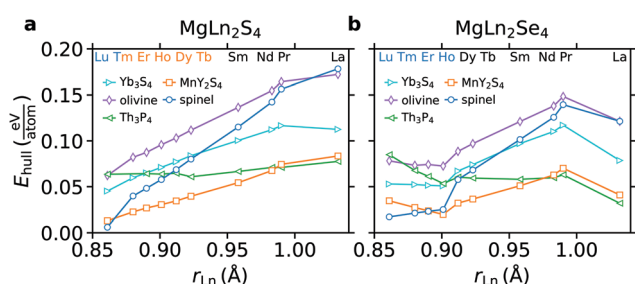


Fig. 5 Stability with respect to competing phases, E_{hull} for each sulphide (a) and selenide (b) in a variety of crystal structures common to AB₂X₄-type compounds. The colour of each element at the top of both panels correspond with the experimentally observed crystal structure for that composition.^{27,30} MgTm₂S₄ is coloured for both spinel and MnY₂S₄ because both crystal structures have been reported. Elements coloured black indicate no experimentally known crystal structure.

computing resources through the National Energy Research Scientific Computing Center (NERSC), a U.S. Department of Energy Office of Science User Facility operated under Contract No. DE-AC02-05CH11231, and the Extreme Science and Engineering Discovery Environment (XSEDE), which is supported by National Science Foundation grant number ACI-1548562.

Conflicts of interest

There are no conflicts to declare.

Notes and references

- 1 P. Canepa, G. Sai Gautam, D. C. Hannah, R. Malik, M. Liu, K. G. Gallagher, K. A. Persson and G. Ceder, *Chem. Rev.*, 2017, **117**, 4287–4341.
- 2 J. Muldoon, C. B. Bucur and T. Gregory, *Chem. Rev.*, 2014, **114**, 11683–11720.
- 3 J. Bitenc and R. Dominko, *Front. Chem.*, 2018, **6**, 634.
- 4 H. D. Yoo, I. Shterenberg, Y. Gofer, G. Gershinsky, N. Pour and D. Aurbach, *Energy Environ. Sci.*, 2013, **6**, 2265–2279.
- 5 P. Canepa, S.-H. Bo, G. Sai Gautam, B. Key, W. D. Richards, T. Shi, Y. Tian, Y. Wang, J. Li and G. Ceder, *Nat. Commun.*, 2017, **8**, 1759.
- 6 T. Famprikis, P. Canepa, J. A. Dawson, M. S. Islam and C. Masquelier, *Nat. Mater.*, 2019, **18**, 1278–1291.
- 7 Y. Wang, W. D. Richards, S. P. Ong, L. J. Miara, J. C. Kim, Y. Mo and G. Ceder, *Nat. Mater.*, 2015, **14**, 1026–1031.
- 8 Z. Rong, P. Xiao, M. Liu, W. Huang, D. C. Hannah, W. Scullin, K. A. Persson and G. Ceder, *Chem. Commun.*, 2017, **53**, 7998–8001.
- 9 Z. Rong, R. Malik, P. Canepa, G. Sai Gautam, M. Liu, A. Jain, K. Persson and G. Ceder, *Chem. Mater.*, 2015, **27**, 6016–6021.
- 10 M. Liu, Z. Rong, R. Malik, P. Canepa, A. Jain, G. Ceder and K. A. Persson, *Energy Environ. Sci.*, 2015, **8**, 964–974.
- 11 G. Sai Gautam, P. Canepa, A. Abdellahi, A. Urban, R. Malik and G. Ceder, *Chem. Mater.*, 2015, **27**, 3733–3742.
- 12 I. D. Brown, *Acta Crystallogr., Sect. B: Struct. Sci.*, 1988, **44**, 545–553.
- 13 V. V. Kulish, D. Koch and S. Manzhos, *Phys. Chem. Chem. Phys.*, 2017, **19**, 6076–6081.
- 14 M. Liu, A. Jain, Z. Rong, X. Qu, P. Canepa, R. Malik, G. Ceder and K. A. Persson, *Energy Environ. Sci.*, 2016, **9**, 3201–3209.
- 15 M. Patrie, J. Flahaut and L. Domage, *C. R. Hebd. Seances Acad. Sci.*, 1964, **258**, 2585–2586.
- 16 W. M. Yim, A. K. Fan and E. J. Stofko, *J. Electrochem. Soc.*, 1973, **120**, 441.
- 17 M. Guittard, C. Souleau and H. Farsam, *C. R. Hebd. Seances Acad. Sci.*, 1964, **259**, 2847–2849.
- 18 J. C. Bachman, S. Muy, A. Grimaud, H.-H. Chang, N. Pour, S. F. Lux, O. Paschos, F. Maglia, S. Lupart, P. Lamp, L. Giordano and Y. Shao-Horn, *Chem. Rev.*, 2016, **116**, 140–162.
- 19 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 20 D. Sheppard, R. Terrell and G. Henkelman, *J. Chem. Phys.*, 2008, **128**, 134106.
- 21 J. Sun, M. Marsman, G. I. Csonka, A. Ruzsinszky, P. Hao, Y.-S. Kim, G. Kresse and J. P. Perdew, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2011, **84**, 035117.
- 22 R. D. Shannon, *Acta Crystallogr., Sect. A: Cryst. Phys., Diffraction, Theor. Gen. Crystallogr.*, 1976, **32**, 751–767.
- 23 V. M. Goldschmidt, *Trans. Faraday Soc.*, 1929, **25**, 253–283.
- 24 J. H. Yang, D. A. Kitchaev and G. Ceder, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2019, **100**, 035132.
- 25 C. J. Bartel, A. W. Weimer, S. Lany, C. B. Musgrave and A. M. Holder, *npj Comput. Mater.*, 2019, **5**, 4.
- 26 S. P. Ong, L. Wang, B. Kang and G. Ceder, *Chem. Mater.*, 2008, **20**, 1798–1807.
- 27 O. Müller and R. Roy, *The major ternary structural families*, Springer-Verlag, 1974.
- 28 W. Sun, S. T. Dacek, S. P. Ong, G. Hautier, A. Jain, W. D. Richards, A. C. Gamst, K. A. Persson and G. Ceder, *Sci. Adv.*, 2016, **2**, e1600225.
- 29 A. Navrotsky, C. Ma, K. Lilova and N. Birkner, *Science*, 2010, **330**, 199.
- 30 J. Flahaut, *Progress in Science and Technology of the Rare Earths*, Pergamon Press, 1968, pp. 209–283.
- 31 W. Kohn and L. J. Sham, *Phys. Rev.*, 1965, **140**, A1133–A1138.
- 32 G. Kresse and J. Furthmüller, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1996, **54**, 11169.
- 33 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- 34 G. Kresse and D. Joubert, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1999, **59**, 1758–1775.
- 35 D. Sheppard, R. Terrell and G. Henkelman, *J. Chem. Phys.*, 2008, **128**, 134106.
- 36 J. Sun, M. Marsman, G. I. Csonka, A. Ruzsinszky, P. Hao, Y.-S. Kim, G. Kresse and J. P. Perdew, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2011, **84**, 035117.
- 37 A. Jain, S. P. Ong, G. Hautier, W. Chen, W. D. Richards, S. Dacek, S. Cholia, D. Gunter, D. Skinner, G. Ceder and K. A. Persson, *APL Mater.*, 2013, **1**, 011002.